


Measuring protocol airflow resistance according to DIN EN 29053 (ISO 9053)

Measurement of specific airflow resistance R_s

Measuring sample:

Name: CAMPARI 126
Description: acoustic fabric
Manufacturer: création baumann Weberei und Färberei AG
CH-4901 Langenthal
Client of measurement: manufacturer



**AKUSTIK
FORSCHUNG**

Research & Development - Test - Consultancy

Measuring conditions:


Standard: DIN EN 29053: Materials for acoustical applications; Determination of airflow resistance (ISO 9053)
Method: direct-airflow method, measurement at 10 different airflow velocities and extrapolation to an airflow velocity of 0,5 mm/s
Specimen holder: round, 100 mm diameter
Temperature: 21 °C
Relative humidity: 61%
Measurement date: 2007-08-01

Specimen:

Total number: 1
Shape: specimen (ca. 200 mm x 180 mm) fit in specimen holder
Effective cross section: 78,54 cm²

Single results:

Specimen	Nr.1		
	u	Δp	R_s
Measuring values	47,2	11,6	246
	42,1	10,3	244
	38,0	9,2	242
	34,4	8,2	240
	30,8	7,4	239
	27,4	6,5	238
	24,1	5,7	235
	20,7	4,9	236
	17,4	4,1	233
	14,2	3,3	234
Extrapolation	0,5		228

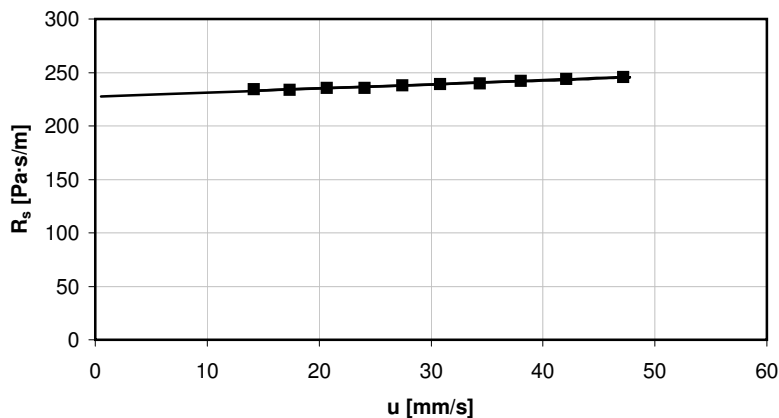

Airflow velocity u in mm/s, pressure difference Δp over specimen in Pa, specific airflow resistance R_s in Pa·s/m

Measuring result:

Specific airflow resistance $R_s = 228 \text{ Pa·s/m}$

Gesellschaft für Akustikforschung Dresden mbH
Stauffenbergallee 15
01099 Dresden
Phone: +49 (0)351 811309-0, Fax: -9

Report-No.: 007106-02
Editor: C. Schulze
Date: 2007-01-22